Common Sea

### **GEOSTATS PTY LTD**


Mining Industry Consultants
Reference Material Manufacture and Sales

Certified Geochem Base Metal Reference Material Product Code

## **GBM920-9**

# Certified Control Values

### **Total Digest**

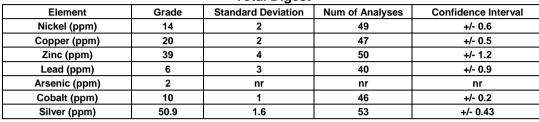

### **Partial Digest**

Element	Grade	Standard Deviation	Num of Analyses	Confidence Interval	
Nickel (ppm)	7	1	46	+/- 0.3	
Copper (ppm)	16	1	48	+/- 0.4	
Zinc (ppm)	19	3	51	+/- 0.9 nr	
Lead (ppm)	2	nr	nr		
Arsenic (ppm)	2	nr	nr	nr	
Cobalt (ppm)	3	nr	nr	nr	
Silver (ppm)	50.8	1.8	66	+/- 0.45	

#### **CRM Details**

	Neutron Activation		Major Elements by	
Control Statistic Details	Analysis Results (ppm,		Fusion / XRF (%)	
Control statistics were produced from results accumulated in the October-2020	unless otherwi	se noted)		
round robin. The number of results used to certify each analyte is shown in the	Antimony	<0.2	Fe	2.43
table above.	Arsenic	< 0.499	SiO <sub>2</sub>	78.62
	Barium	<100	Al <sub>2</sub> O <sub>3</sub>	8.32
Material Description	Bromine	<2	TiO <sub>2</sub>	0.55
This material is described as a Silver Ore.	Cadmium	<10	MnO	0.05
	Caesium	16	CaO	2.93
	Calcium (%)	nr	Р	0.045
Colour Designation (ISCC-NBS, SP440)	Cerium	6	S	0.02
This material is light gray in colour.	Chromium	56	MgO	1.48
	Cobalt	11	K <sub>2</sub> O	2.51
<u>Usage</u>	Europium	<0.5	Na <sub>2</sub> O	1.65
This product is for use in the mining industry as a reference material for	Gold (ppb)	544	LOI1000	0.13
monitoring and testing the accuracy of laboratory assaying.	Hafnium	10		
	Iridium (ppb)	<50	Neutron Act	ivation
Preparation and Packaging	Iron (%)	2.5	Analyses an	d Fusion /
All CRMs are dried in an oven for a minimum of 12 hours at 110°C. The dry	Lanthanum	3	XRF Analys	es are
material is then pulverised to better than 75 micron (nominal mean of 45	Lutetium	0.2	single results and are	
micron) using an air classifier. The material is then homogenised and stored in	Mercury	nr	· ·	
a sealed, stable container ready for final packaging.	Molybdenum	50	indicative only. These	
	Neodymium	nr	are provided	for matrix
Materials are statistically sampled from stores, then packaged into either heat	Nickel	<20	identification	purposes.
sealed, air tight, plastic pulp packets or screw top sealed plastic containers	Potassium (%)	nr		
ready for distribution. All packaging has been chosen to ensure minimal	Rubidium	421	'nr': Not Rep	orted
contamination from outside sources during shipment, use and storage.	Samarium	1.5		
	Scandium	8.7		
Assay Testwork	Selenium	<10		
All standards are tested thoroughly in the Geostats bi-annual laboratory survey.	Silver	53		
This involves assaying by multiple laboratories from around the world. Results	Sodium (%)	1.16		
are compiled into a comprehensive report detailing statistics for each standard.	Strontium	nr		
Assay distributions are checked and processed statistically, producing	Tantalum	<2		
monitoring statistics for these standards. Materials are tested regularly to	Tellurium	<20		
ensure stability and homogeneity.	Terbium	<1		
	Thorium	0.7		
<u>Stability</u>	Tin	<200		
This product remains stable in its original packaging, away from direct sunlight.	Tungsten	<2		
	Uranium	<2		
Material Safety	Ytterbium	1.1		
This product is not hazardous and non-toxic.	Zinc	<200		
	Zirconium	<500		

20 Hines Road, O'Connor, Western Australia 6163
Phone: +61 8 9314 2566 | Email: info@geostats.com.au
Website: www.geostats.com.au